

**SELAC J
 SUPERDURABLE POLYESTERS**

Glossy - Semiglossy - Semimatt - Matt - Metallic and tridimensional effect

DESCRIPTION

Thermosetting powder coatings based on special carboxylated polyester resins resins crosslinked with suitable non-toxic hardeners and exempt from any dangerous substances .
 Only resins and pigments of top quality are used and all formulations are especially especially designed to fulfill the highest expectations in terms of colour stability , gloss retention and corrosion resistance required by the architectural market .
 Thanks to excellent aesthetical properties they satisfy the most severe decorative standards.
 The application is possible with corona and tribo electrostatic systems .

GENERAL PROPERTIES

Outstanding resistance to ageing in outdoor environments
 Good mechanical properties
 Very good corrosion resistance
 Excellent aesthetic properties

SERIES AND FINISHES


- Selac J51 : Glossy class 2 / category 3
 Qualicoat license P-1186
- Selac J52 : Semiglossy class 2 / category 2
- Selac J54 : Matt class 2 / category 1
- Selac J57 : Textured class 2 / category

COLOURS AND EFFECTS

Possibility of a complete colour range
 Gloss range from 20 up to 95 gloss
 Smooth or fine textured finish
 Metallic effects possible in dry-blend or bonded versions
 Salt & pepa and mixcolor
 Neutral clearcoat
 Wide possibility of taylor-made versions on demand

CURING CONDITIONS

Drafts interpretation
 To obtain functional , optical and aesthetic properties mentioned in TDS the curing schedule adopted for the products must be in any point of the draft area comprised between the curves of minimum and maximum .
Times always refer to object temperature (PMT) , being the heating time variable from item to item and from plant to plant .

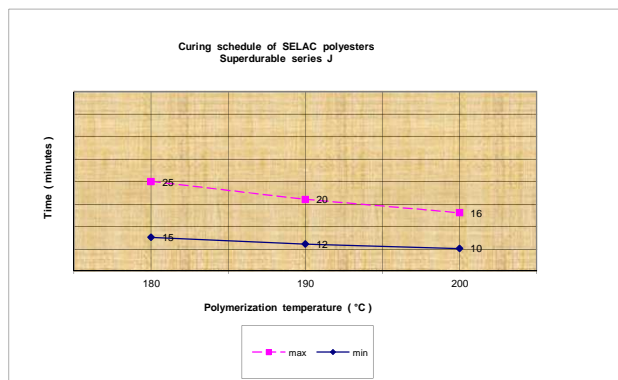

Minimal conditions (PMT)
 15' @ 180°C - 12' @ 190°C - 10' @ 200°C

**SELAC J
SUPERDURABLE POLYESTERS**

Glossy - Semiglossy - Semimatt - Matt - Metallic and tridimensional effect

SUPPORT PREPARATION

Painting must be done on clean support , free from oil , grease , oxidation , residuals of working , welding and rinsing processes , and any contaminating agent must be avoided .
Iron and steel : iron or zinc salts phosphatization
Aluminium : cromatation or chrome-free pretreatment are recommended
Hot dipping galvanized steel : according with the item adopt mechanical treatment , phosphatization or chromatation process .

THICKNESS

Minimal recommended thickness is 60 microns , but in any case the coating layer must completely cover any surface roughness , especially in case of sandblasted supports .
For fine textured products the minimal suggested thickness is 80 micron .

**APPLICATION METHODS
AND RECYCLE**

The application is possible with manual or automatic electrostatic devices , both corona and tribo .
Overspray can be recycled in the fresh powder and re-used , but the use of integral recycle is not recommended at all ; do not exceed 25% and maintain a constant feeding of fresh powder .
On metallic products an indicative ratio is 10% , but an unproper management of the recycle may result in remarkable variations of the effect , therefore it must be evaluated in each single case ; please contact arsonsisi s.p.a. and refer to the technical informative note about application of metallic .

TECHNICAL FEATURES

Specific gravity : 1,3 to 1,5 g/cc , according colour and formula
Theoretical yield at 60 micron : 13 to 11 sqm/kg
according colour and formula
Brilliance range at 60° : 20 to 95
Average particle size (laser Malvern) : 32 - 45 micron
X99 particle size (laser Malvern) : 95 - 150 micron
***** **NOTE** : **taylor-made particle size distributions**
are possible on demand

**MECHANICAL
PROPERTIES**

Test conditions : trials are made on normalized UNI 5961 panels 0,6 mm thick , degreased with solvent , coated with 70 - 80 micron of powder completely cured .
Mentioned results are obtained under controlled lab conditions ; therefore these values are merely indicative and must be confirmed in the actual use conditions under the responsibility of each single user .

Minimal polymerization conditions (PMT)

15' @ 180°C - 12' @ 190°C - 10' @ 200°C

Thickness : 70 - 80 micron .

Direct impact : min. 30 Nm (ISO 6272)

Erichsen embossing (ISO 1520) : min. 4 mm

Cylindrical mandrel (ISO 1519/73) : pass 3/16" = 5 mm

Adhesion (ISO 2409) : GT 0/1

Buchholz hardness (ISO 2815) : min. 85

Pencil hardness (ASTM D3363) : H - 2H

**SELAC J
SUPERDURABLE POLYESTERS**

Glossy - Semiglossy - Semimatt - Matt - Metallic and tridimensional effect

**CORROSION
AND DURABILITY**

Test conditions : trials are made on normalized UNI 5961 panels 0,6 mm thick , treated by microcrystalline zinc salts phosphatization , or on AA 5005-H24 chromated aluminium panels , coated with 70 - 80 micron of powder completely cured .

Mentioned results are obtained under controlled lab conditions ; therefore these values are merely indicative and must be confirmed in the actual use conditions under the responsibility of each single user .

Salt spray test (ISO 3768 / ASTM B117)

Support UNI 5961 steel treated by zinc phosphate

After 1000 hours rust penetration at the cross-hatch : max. 4 mm

Saline-acetic spray test (ISO 9227)

Support UNI 5961 steel treated by zinc phosphate

After 1000 hours rust penetration at the cross-hatch : max. 16 mm

Humidostatic test (ISO 6270)

Support UNI 5961 steel treated by zinc phosphate

After 1000 hours no film variation

Exposure in sulphur dioxide according " Kesternich test " (ISO 3231)

After 24 hours no blistering , no colour variation , no gloss variation

Accelerated whathering (EN ISO 11341)

After 1000 hours of test the gloss retention is higher than 90% of starting value and colour variation fulfills Qualicoat specifications

Exterior durability

After 36 months of exposure in Florida the gloss retention is higher than 50% of starting value and colour variation fulfills Qualicoat specifications

Chemical resistances at room temperature (25+/-3°C)

Generally good versus diluted acids and diluted alkalis

Sufficient versus aromatics , moderate versus ketons and alogenated

The behaviour versus very aggressive or concentrated agents or under different conditions must be verified by the user

**STORAGE
AND STABILITY**

Products must be stored in the original sealed packagings , in a cool and dry place and at a temperature not exceeding 30°C .

In these conditions products **SELAC J polyesters SD** are stable for a period of 36 months .

Matt versions J54 are stable for a period of 12 months .

Always consult the specific TDS of each single product or contact arsonsisi s.p.a.

RECOMMENDATIONS

These informations are given on the base of our best experience as well as the one of specialized laboratories and they are continuously updated , nevertheless the user has the complete responsibility to apply and to experiment the products according its own specific necessities .

This document has the intention to describe and summarize the main properties of arsonsisi products , but in no case it can be considered as a warranty for them .

Further informations about application of metallic effects , maintenance of goods coated with homologated polyesters or availability of special versions are mentioned in specific technical integrative notes .